

Adamite Steel Base

Field of Application

Mill Type	Position
Rail, Heavy and Medium Section Mills	Roughing and Intermediate Stands and Universal Rings
Small Section Mills	Roughing Stands
Bar and Rebar Mills	Roughing Stands

Properties

Hardness Range	45-60 ShC
Tensile Strength	500 to 650 MPa
Bending Strength	900 - 1300 MPa
Young's Modulus	≈200.000 MPa

Adamite steel based rolls and rings are classified as high-carbon steels, typically containing 1.4-2.2 wt. % carbon. Their microstructure consists of a pearlitic matrix with primary carbides formed during solidification. A homogeneous distribution of fine secondary carbides is also developed within the matrix as a result of normalization heat treatment. In addition to providing adequate wear resistance, the presence of a discontinuous carbide network contributes to high toughness, making these products particularly suitable for stands operating under high rolling forces. Adamite rolls are generally manufactured by static casting, whereas Adamite rings can be produced by both static and centrifugal casting methods.

Product Highlights


- Spall resistant
- High strength
- Low hardness drop through depth



Chemical Composition:


	C	Mn	Si	P	S	Ni	Cr	Mo
Min	1.40	0.40	0.30	0.00	0.00	0.50	0.70	0.20
Max	2.20	1.00	1.00	0.05	0.05	1.70	1.80	0.80

Microstructure:

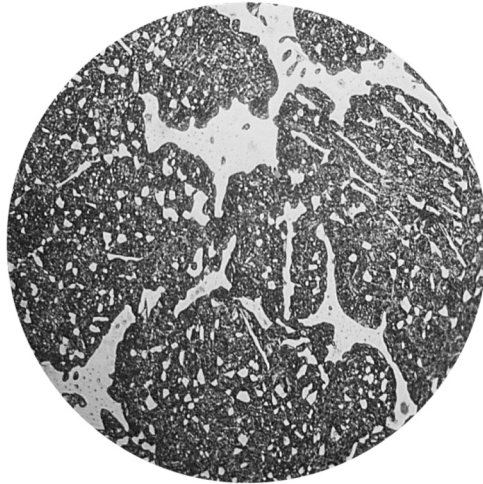

400 X – etched

Hardness Graph:

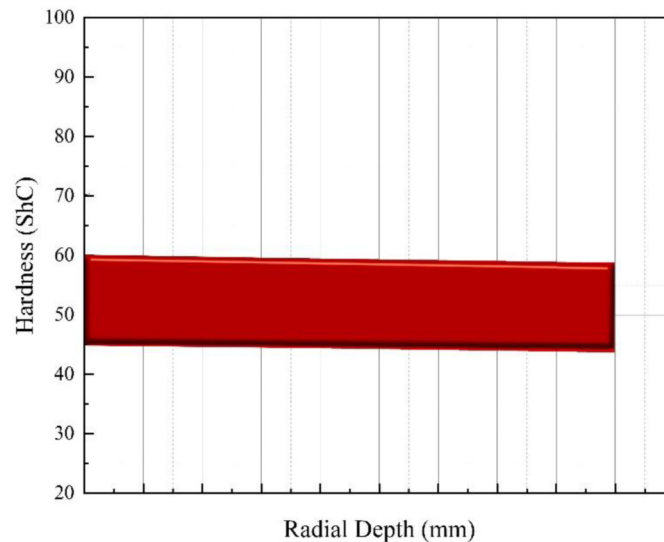

Contact Us:

Contact Us:

Roll Nova – Izmir / Turkey

Homepage: www.rollnova.com

Email: sales@rollnova.com